

Environmental Product Declaration

Pre-painted Galvalume Product, Tarapur Plant, JSWSCPL

ISO 14020:2000, ISO 14025:2006, ISO 14040:2006, ISO 14044:2006, EN 15804:2012+A2:2019



| EPD Registration Number | Publication Date | Validity Date | Geographical Scope |
|-------------------------|------------------|---------------|--------------------|
| S-P-06490 | 2023-08-07 | 2028-08-06 | India |

1. Introduction

Founded in 2013, JSW Steel Coated Products Limited (JSWSCPL) is India's largest manufacturer and exporter of colour-coated steel products with a total production capacity of 3.12 MTPA with the capability to produce 1.4 MTPA of Colour Coated Steel. The vision of the company "Nurture Leadership in Coated Products by creating value for Stakeholders in an Environmentally Sustainable way" has been developed from the parent company. JSWSCPL is a wholly owned subsidiary of JSW Steel, having state of the art manufacturing facilities at Vasind, Tarapur & Kalmeshwar in Maharashtra. The facilities at Vasind & Tarapur plants are located near major ports & Kalmeshwar plant is centrally located near Nagpur to serve customers across the nation. With a strong focus on sustainability and innovation, JSWSCPL dominates the value-added product market. The product portfolio is vast as the products can be obtained in different hues, textures and finishes.



Following are the products offered by JSWSCPL, Tarapur:

- Galvanized Steel.
- Galvalume Steel.
- Pre painted Galvanized Steel (PPGI).
- Pre painted Galvalume Steel (PPGL).
- Tinplate

The Company has been at the forefront of state-of-the-art, cutting-edge technology, research and innovation while laying the foundation for long-term growth. JSWSCPL have strategic collaborations with global technology leaders to offer high-value special steel products for various applications across construction, infrastructure, automobile, appliances and other sectors.

JSW Steel Coated Products Limited (JSWSCPL) is committed towards their environmental, social and governance (ESG) goals to create sustainable long-term value for all stakeholders. With sustainability at the core of the corporate strategy, JSWSCPL strive to be a force for good, driven by responsible business conduct that enhances the lives of communities and nurtures the environment.

Thinkstep Sustainability Solutions Pvt. Ltd, a Sphera Company (formerly thinkstep AG). has been entrusted to conduct Life Cycle Assessment for JSW Steel coated products as per the ISO 14040/44. The LCA model was created using the GaBi ts Software system for life cycle engineering, developed by Sphera (formerly thinkstep AG).



2. General Information

Environmental Product Declaration in accordance with ISO 14025:2006 and EN 15804:2012+A2:2019/AC:2021.

2.1 EPD, PCR, LCA Information

Table 1: EPD Information

| Programme | The International EPD System, www.environdec.com | |
|---------------------------------|---|---|
| Program operator | EPD International AB Box 210 60, SE-100 31 Stockholm, Sweden info@environdec.com | Indian Regional Hub www.environdecindia.com |
| Declaration holder ¹ | Name - Mr. Swaroop Banerjee JSW Steel Coated Products Limited (JSWSCPL) JSW Centre - 6th Floor, Bandra Kurla Complex Bandra (East), Mumbai – 400051, Maharashtra Email - swaroop.banerjee@jsw.in Website - www.jsw.in | |
| Product | Pre-painted Galvalume | |
| CPC Code | 412 (Version 2.1) | |
| Geographical scope | India | |
| Reference standards | ISO 14020:2001, ISO 14025:2006, EN 15804:2012+A2:2019 | |

Table 2: PCR Information

| | |
|---------------|--|
| Reference PCR | 'Construction Products and Construction Services' Version 1.2.5, 2019:14 |
| Date of Issue | 2022-07-08 (Version 1.2.5) (VALID UNTIL: 2024-12-20) |

Table 3: Verification Information

| | |
|-------------------------------|--|
| Demonstration of verification | External, independent verification |
| Third party verifier | Dr. Hüdai Kara, Metsims Sustainability Consulting, 4 Clear Water Place, Oxford OX2 7NL, UK Email: hudai.kara@metsims.com |

Table 4: LCA Information

| | | |
|---------------------|---|---|
| Title | Environmental Product Declaration of Pre-painted Galvalume | |
| Author | Dr. Rajesh Kumar Singh Thinkstep Sustainability Solutions Pvt. Ltd., a Sphera Company 707, Meadows, Sahar Plaza, Andheri Kurla Road, Andheri East, Mumbai, India - 400059 Email: rsingh@sphera.com |  |
| Reference standards | ISO 14040/44 standard | |

¹ EPD owner has the sole ownership, liability, and responsibility for the EPD.

2.2 Reference Period of EPD Data

The reference period for the primary data (foreground data) used within this EPD is FY April 2021 - March 2022. The background data used in the study have been applied through GaBi datasets which are less than 5 years old.

2.2 Geographical Scope of EPD Application

The geographical scope of this EPD is India.

2.4 Additional Information about EPD

This EPD provides information for the Pre-painted Galvalume product at JSW Steel Coated Products Limited's Tarapur plant in India. The EPD is in accordance with ISO 14025 and EN 15804+A2. EPD of construction products may not be comparable if they do not comply with EN 15804+A2. The Life Cycle Assessment (LCA) study carried out for developing this EPD for Galvanized steel product is done as per ISO 14040 and ISO 14044 requirements.

Product Category Rules (PCR) for the assessment of the environmental performance of steel products is PCR for 'Construction Products and Construction Services', Version 1.2.5, 2019:14.

This PCR is applicable to the product "Pre-painted Galvalume" complying with the standard EN 15804+A2 (Sustainability of construction works - Environmental product declarations - Core rules for the product category of construction products).

EPDs within the same product category but registered in different EPD programmes, or not compliant with EN 15804, may not be comparable. For two EPDs to be comparable, they must be based on the same PCR (including the same version number) or be based on fully-aligned PCRs or versions of PCRs; cover products with identical functions, technical performances and use (e.g. identical declared/functional units); have equivalent system boundaries and descriptions of data; apply equivalent data quality requirements, methods of data collection, and allocation methods; apply identical cut-off rules and impact assessment methods (including the same version of characterisation factors); have equivalent content declarations; and be valid at the time of comparison. For further information about comparability, see EN 15804 and ISO 14025.

3. Product Description and System Boundaries

3.1 Product Identification and Usage

JSWSCPL's Colour Coated product offering combines the strength of steel, the beauty of paint and enhanced corrosion resistance in an unbeatable package. The pre-painted corrugated sheets and profiles are branded as JSW Coloureon (Colour coated galvanised sheets) and JSW Coloureon Plus (55% aluminium-zinc alloy colour coated steel sheets). Our pre-painted products are available in a variety of paint systems, including Regular Modified Polyester, Silicon Modified Polyester, Super Durable Polyester, Poly Vinylidene Fluoride and Vinyl Coated Metal.



Pre-Painted Galvalume:

With the help of up-to-date technology that includes the first appliance grade manufacturing line for colour coated products in India, it is ensured that the product is all-around superior in quality. The base metal has the first layer of primer coating on the top and the bottom surface for superior adhesion with the paint system, which is toxin-free. The final paint coating provides additional protection against harsh weather conditions and other factors that impact its longevity. The superior coating technology is designed to resist cracking and peeling, even during heavy forming operations. Thanks to all these factors, JSW Coloureon and JSW Coloureon Plus have a long life and are recyclable if eventually replaced.



Table 5: Content Declaration

| Product Component | Weight, % | Biogenic material, weight % and kg C/kg |
|---------------------|-----------|---|
| Steel | 92.55% | – |
| Zinc | 1.37% | - |
| Al-Si alloy | 1.93% | - |
| Polymer | 1.44% | - |
| Pigment | 2.71% | - |
| Sum | 100% | |
| Packaging Materials | Weight, % | Biogenic material, weight % and kg C/kg |
| Paper | 32.00% | 0.42 |
| Plastic | 68.00% | - |
| Sum | 100% | |

3.2 System boundary

Figure 1 given below represents system boundary diagram of the study.

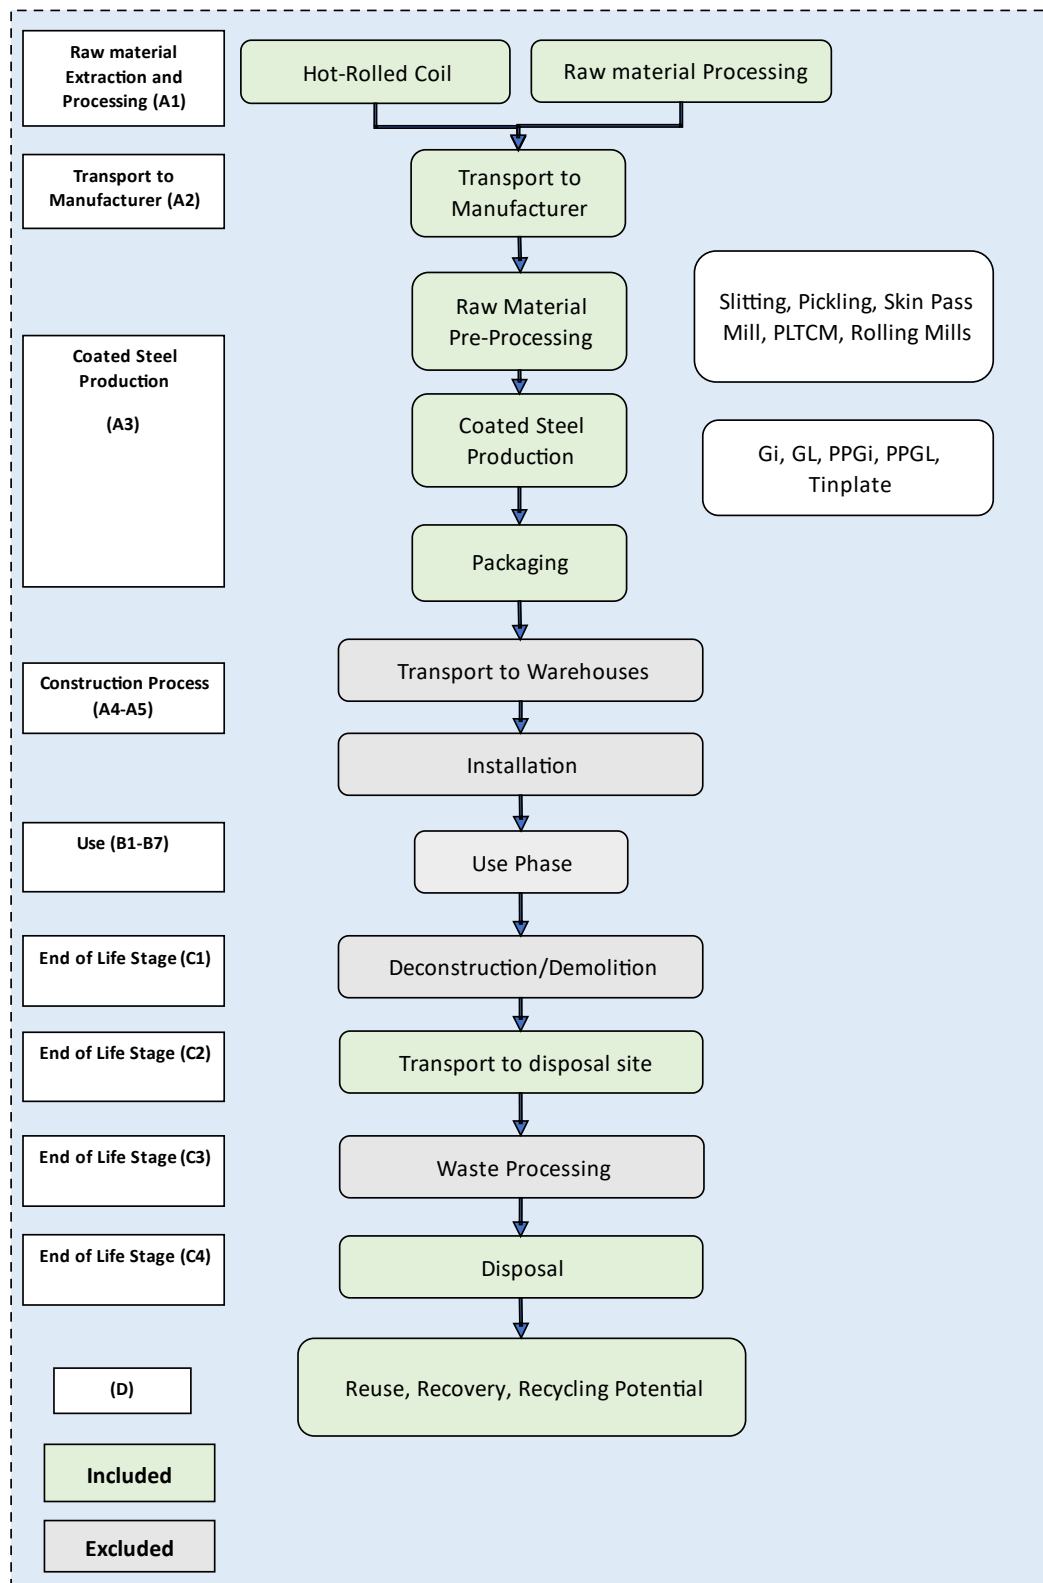


Figure 1: System Boundary (Schematic)

3.3 Process Description

JSW Steel Coated Products Limited (JSWSCPL), Tarapur was acquired in 1982 and was the first plant to have a galvanising line commissioned for it. It is also recognised as India's largest producer and exporter of coated products and features a 30MW captive power plant with clients spread across Europe, North and South America, Africa, and the Middle East. Tarapur has both the technology and the equipment to cater to every need.

JSWSCPL's Tarapur works is largest coated steel plant in a single location specialising in manufacturing of ultra-thin coated products. The plant offers coated products catering to several sectors and located about 100 kms from Mumbai. The plant produces pre-painted galvanized/galvalume, galvanized and bare galvalume steel. It has unique service centre facility to meet the customised requirements of various segments. The plant has zero discharge facility having multi-effect evaporator system for effluent treatment.

Products are manufactured using multiple Processes. JSW's Vijayanagar, Dolvi and other Plants provides the Hot-Rolled Coil (HRC) Steel to manufacturing site for further processing. This HRC is firstly taken into slitting and pickling process where, cutting of sheets as per desired dimensions and removal of impurities takes place. After that, fraction of output generated from pickling process is sent to skin pass mill and some percentage share of that, is sent into three rolling mills where, improvement in surface texturing, surface flatness and mechanical properties takes place. Then the cold rolled coils are being sent for Galvanizing processes to produce Galvalume. Further, this product is sent to colour coating line for manufacturing of Pre-painted Galvalume product followed by packaging process.

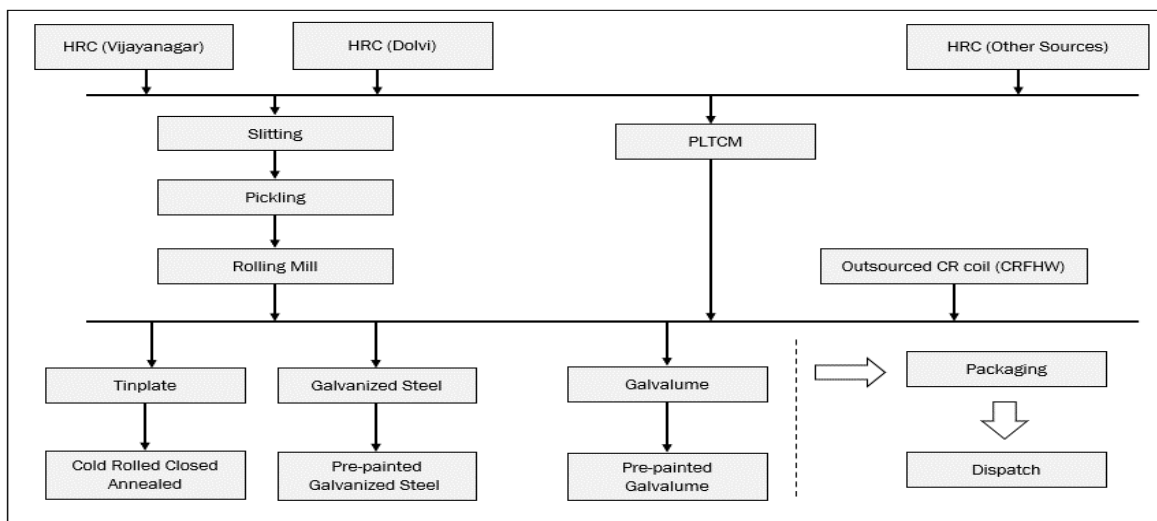


Figure 2: Manufacturing Process at Tarapur

4. LCA

4.1 Information Sources and Data Quality

It is important that data quality is in accordance with the requirements of the LCA's goal and scope. This is essential to the reliability of LCA and achievement of the intended application. The quality of the LCI data for modelling the life cycle stages have been assessed according to ISO 14040:2006. Data quality is judged by its precision (measured, calculated or estimated), completeness (e.g., are there unreported emissions?), consistency (degree of uniformity of the methodology applied on an LCA serving as a data source) and representativeness (geographical, time period, technology). Primary data collected using data collection questionnaires was used for the study and for upstream processes GaBi 10.6 Modelling database 2021 was used.

4.2 Methodological Details

4.2.1 Declared unit

The declared unit for the EPD is 1 tonne of Pre-painted Galvalume manufactured at JSW Steel Ltd., Tarapur Plant, India.

4.2.2 Selection of application of LCIA categories

A list of relevant impact categories and category indicators is defined and associated with the inventory data. The environmental impact per declared unit for the following environmental impact categories were reported in the EPD according with EN15804+A2:2019 (Table 6), and divided into Production, Installation, Use stage, End-of-Life module and Credits & charges outside system boundary (if included).

Table 6. Environmental impacts indicators for EN15804+A2:2019

| Impact category | Indicator | Unit |
|---|---|----------------------------|
| Climate change – total | Global Warming Potential total (GWP-total) | kg CO ₂ eq. |
| Climate change - fossil | Global Warming Potential fossil fuels (GWP-fossil) | kg CO ₂ eq. |
| Climate change - biogenic | Global Warming Potential biogenic (GWP-biogenic) | kg CO ₂ eq. |
| Climate change - luluc | Global Warming Potential land use and land use change (GWP-luluc) | kg CO ₂ eq. |
| Ozone Depletion | Depletion potential of the stratospheric ozone layer (ODP) | kg CFC-11 eq. |
| Acidification | Acidification potential, Accumulated Exceedance (AP) | Mole of H ⁺ eq. |
| Eutrophication aquatic freshwater | Eutrophication potential, fraction of nutrients reaching freshwater end compartment (EP-freshwater) | kg P eq. |
| Eutrophication aquatic marine | Eutrophication potential, fraction of nutrients reaching marine end compartment (EP-marine) | kg N eq. |
| Eutrophication terrestrial | Eutrophication potential, Accumulated Exceedance (EP-terrestrial) | Mole of N eq. |
| Photochemical ozone formation | Formation potential of tropospheric ozone (POCP) | kg NMVOC eq. |
| Depletion of abiotic resources - minerals and metals ² | Abiotic depletion potential for non-fossil resources (ADP- minerals & metals) | kg Sb eq. |
| Depletion of abiotic resources - fossil fuels ² | Abiotic depletion for fossil resources potential (ADP-fossil) | MJ |
| Water use ² | Water (user) deprivation potential, deprivation-weighted water consumption (WDP) | m ³ world eq. |

The consumption of natural resources per declared or function unit is reported in the EPD. Input parameters, according with EN15804+A2, describing resource use are shown in Table 7.

Table 7. Natural resources use parameters

| Parameter | Unit |
|---|----------------|
| Renewable primary energy as energy carrier (PERE) | MJ |
| Renewable primary energy resources as material utilization (PERM) | MJ |
| Total use of renewable primary energy resources (PERT) | MJ |
| Non-renewable primary energy as energy carrier (PENRE) | MJ |
| Non-renewable primary energy as material utilization (PENRM) | MJ |
| Total use of non-renewable primary energy resources (PENRT) | MJ |
| Use of secondary material (SM) | kg |
| Use of renewable secondary fuels (RSF) | MJ |
| Use of non-renewable secondary fuels (NRSF) | MJ |
| Net freshwater Use (FW) | m ³ |

Table 8. Output flows and waste categories parameters

| Parameter | Unit |
|-------------------------------------|------|
| Hazardous waste disposed (HWD) | kg |
| Non-hazardous waste disposed (NHWD) | kg |
| Radioactive waste disposed (RWD) | kg |
| Components for re-use (CRU) | kg |
| Materials for recycling (MFR) | kg |
| Materials for energy recovery (MER) | kg |
| Exported electrical energy (EEE) | MJ |
| Exported thermal energy (EET) | MJ |

Table 9. Additional parameters

| Impact category | Indicator | Unit |
|---|--|--------------------|
| Particulate matter emissions | Potential incidence of disease due to PM emissions (PM) | Disease incidences |
| Ionising radiation ¹ | Potential Human exposure efficiency relative to U235 (IRP) | kBq U235 eq. |
| Eco-toxicity (freshwater) ² | Potential Comparative Toxic Unit for ecosystems (ETP - fw) | CTUe |
| Human toxicity, cancer effects ² | Potential Comparative Toxic Unit for humans (HTP - c) | CTUh |
| Human toxicity, non-cancer effects ² | Potential Comparative Toxic Unit for humans (HTP - nc) | CTUh |
| Land use related impacts/ Soil quality potential ² | Potential soil quality index (SQP) | Pt |

**Disclaimer 1 – This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and from some construction materials is also not measured by this indicator.*

**Disclaimer 2 – The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experienced with the indicator.*

4.2.3 Cut-off Criteria

Criteria were set out in the original study for the recording of material flows and to avoid the need to pursue trivial inputs/outputs in the system. These are outlined below:

1. All energetic inputs to the process stages were recorded, including heating fuels and electricity.
2. The sum of the excluded material flows must not exceed 5% of mass, energy, or environmental relevance. However, in reality at least 99.9% of material inputs to each process stage were included.
3. Wastes representing less than 1% of total waste tonnage for given process stages were not recorded unless treated outside of the site.

4.3 Co-Product Allocation

No allocation is applied.

4.4 System Boundaries

The study covers the stages from production of raw materials to the End of Life of the product, excluding the use phase of the product.

The scope covers the ecological information to be divided into raw material production (A1), inbound transportation (A2), Manufacturing (A3), treatment of packaging (A5), transport of dismantled product to EoL site (C2), waste processing (C3), disposal (C4) as well as the end of life stage recycling (D) considerations.

4.4.1 Geographic System Boundaries

The geographical coverage of this study covers the production of Pre-painted galvalume product at JSW Steel Coated Products Limited (JSWSCPL), Tarapur plant in India. Indian specific datasets wherever possible have been adapted and others dataset were chosen from EU if no Indian datasets were available. In addition, imported raw materials are considered along with transport. All the primary data has been collected from JSW Steel Coated Products Limited (JSWSCPL) in cooperation with experts from Sphera (formerly Thinkstep AG).

4.4.2 Temporal System Boundaries

The data collection is related to one year of operation and the year of the data is indicated in the questionnaire for each data point. The data was derived for the FY April 2021 – March 2022. It is believed to be representative of steel production during this time frame.

4.4.3 Technology coverage

In the present study, Hot-Rolled Coil, Cold rolled Coil steel is the major raw material used in the production of the Pre-painted Galvalume.

4.5 End-of-life phase

Steel is completely recyclable. Therefore, it is important to consider recycling in LCA studies involving steel, namely the steel scrap that is recycled from a final product at the end of its life. In addition, steel is a vital input to the steelmaking process, and this input of steel scrap should also be considered in LCA studies. Accounting for all these, the End-of -life credit for recycling is applied over 85% of steel (850 kg in 1 ton of steel products).² The landfill is considered as 15% of steel (150 kg in 1 ton of steel products).

² <http://www.worldsteel.org/en/dam/jcr:6a222ba2-e35a-4126-83ab-5ae5a79e6e46/LCA+Methodology+Report.pdf>

4.6 Software and database

The LCA model was created using the GaBi 10.6.0.110 Software system for life cycle engineering, developed by Sphera Solutions Inc. The GaBi database provides the life cycle inventory data for several of the raw and process materials obtained from the upstream system. Detailed database documentation for GaBi datasets can be accessed at:

<https://sphera.com/product-sustainability-gabi-data-search/>

4.7 Comparability

According to the standards, EPDs do not compare the environmental performance of products in the sector. Any comparison of the declared environmental performance of products lies outside the scope of these standards and is suggested to be feasible only if all compared declarations follow equal standard provisions.

| | Production | | | Installation | | Use stage | | | | | | | End-of-Life | | | | Credits & charges outside system boundary |
|----------------------|---------------------|---------------------------|---------------|----------------------------|----------------------------|-------------------|-------------|--------|-------------|---------------|------------------------|-----------------------|-----------------------------|------------------|---|----------|---|
| | Raw material supply | Transport to manufacturer | Manufacturing | Transport to building site | Installation into building | Use / application | Maintenance | Repair | Replacement | Refurbishment | Operational energy use | Operational water use | Deconstruction / demolition | Transport to EoL | Waste processing for reuse, recovery, recycle | Disposal | Reuse, recovery, or recycling potential |
| Module | A1 | A2 | A3 | A4 | A5 | B1 | B2 | B3 | B4 | B5 | B6 | B7 | C1 | C2 | C3 | C4 | D |
| Modules declared | X | X | X | MND | X | MND | MND | MND | MND | MND | MND | MND | X | X | X | X | X |
| Geography | India | | | | | | | | | | | | | | | | |
| Specific data used | | | | - | - | - | - | - | - | - | - | - | - | - | - | - | - |
| Variation - products | NA | | | | | | | | | | | | | | | | |
| Variation - Sites | NA | | | | | | | | | | | | | | | | |

4.8.1 LCIA results for 1 tonne of Pre-painted Galvalume Product

The LCIA results for 1 tonne of Pre-painted Galvalume are given in Table 11 - Table 16.

Table 11. Environmental impacts for 1 tonne of Pre-painted Galvalume

| 1. Environmental impact indicators | | | | | | | |
|---|----------|----------|----------|----------|----------|----------|-----------|
| Parameters | A1-A3 | A5 | C1 | C2 | C3 | C4 | D |
| Climate Change - total [kg CO ₂ eq.] | 4.32E+03 | 9.09E-01 | 0.00E+00 | 3.25E+00 | 0.00E+00 | 2.28E+00 | -1.45E+03 |
| Climate Change, fossil [kg CO ₂ eq.] | 4.30E+03 | 7.27E-01 | 0.00E+00 | 3.24E+00 | 0.00E+00 | 2.27E+00 | -1.45E+03 |
| Climate Change, biogenic [kg CO ₂ eq.] | 1.31E+01 | 1.81E-01 | 0.00E+00 | 8.07E-03 | 0.00E+00 | 7.98E-03 | -8.22E-01 |
| Climate Change, land use and land use change [kg CO ₂ eq.] | 2.80E+00 | 3.07E-05 | 0.00E+00 | 1.69E-04 | 0.00E+00 | 6.66E-03 | -3.28E-02 |
| Ozone depletion [kg CFC-11 eq.] | 1.84E-06 | 2.58E-16 | 0.00E+00 | 2.66E-16 | 0.00E+00 | 8.81E-15 | -3.44E-12 |
| Acidification [Mole of H ⁺ eq.] | 3.75E+01 | 1.44E-04 | 0.00E+00 | 1.93E-02 | 0.00E+00 | 1.62E-02 | -2.58E+00 |
| Eutrophication, freshwater [kg P eq.] | 3.71E-03 | 4.08E-08 | 0.00E+00 | 6.86E-07 | 0.00E+00 | 3.81E-06 | -3.14E-04 |
| Eutrophication, marine [kg N eq.] | 5.55E+00 | 4.39E-05 | 0.00E+00 | 8.68E-03 | 0.00E+00 | 4.19E-03 | -4.97E-01 |
| Eutrophication, terrestrial [Mole of N eq.] | 6.09E+01 | 6.54E-04 | 0.00E+00 | 9.52E-02 | 0.00E+00 | 4.61E-02 | -5.03E+00 |
| Photochemical ozone formation, human health [kg NMVOC eq.] | 1.63E+01 | 1.22E-04 | 0.00E+00 | 1.72E-02 | 0.00E+00 | 1.27E-02 | -2.22E+00 |
| Resource use, mineral and metals [kg Sb eq.] | 1.12E-01 | 3.76E-09 | 0.00E+00 | 4.28E-08 | 0.00E+00 | 2.14E-07 | -3.58E-03 |
| Resource use, fossils [MJ] | 4.55E+04 | 3.41E-01 | 0.00E+00 | 4.30E+01 | 0.00E+00 | 3.01E+01 | -1.41E+04 |
| Water use [m ³ world equiv.] | 2.28E+02 | 9.82E-02 | 0.00E+00 | 9.79E-03 | 0.00E+00 | 2.43E-01 | -3.93E+03 |

Caption: GWP - total = global warming potential; GWP - fossil = global warming potential (fossil fuel only); GWP - biogenic = global warming potential (biogenic); GWP - luluc = global warming potential (land use only); GWP - GHG = global warming potential (greenhouse gases); ODP = ozone depletion; AP = acidification terrestrial and freshwater; EP freshwater = eutrophication potential (freshwater); EP - marine = eutrophication potential (marine); EP - terrestic = eutrophication potential (terrestrial); POCP = photochemical ozone formation; ADPE = abiotic depletion potential (element); ADPF = abiotic depletion potential (fossil); WDP = water scarcity.

Table 12: Environmental impacts (GWP) for 1 tonne of Pre-painted Galvalume Steel

[illegible]

Table 13. Resource use indicators for 1 tonne of Pre-painted Galvalume Steel

[illegible]

Table 14: Output flows and waste categories for 1 tonne of Pre-painted Galvalume

| 3. Output flows and waste categories | | | | | | | |
|--|----------|----------|----------|----------|----------|----------|----------|
| Parameters | A1-A3 | A5 | C1 | C2 | C3 | C4 | D |
| Hazardous waste disposed (HWD) [kg] | 2.17E-05 | 6.15E-11 | 0.00E+00 | 1.98E-10 | 0.00E+00 | 3.20E-09 | 3.09E-06 |
| Non-hazardous waste disposed (NHWD) [kg] | 1.36E+02 | 7.56E-02 | 0.00E+00 | 7.74E-04 | 0.00E+00 | 1.50E+02 | 1.80E+02 |
| Radioactive waste disposed (RWD) [kg] | 1.98E-01 | 1.40E-05 | 0.00E+00 | 9.34E-06 | 0.00E+00 | 3.15E-04 | 1.46E-03 |
| Materials for Recycling (MFR) [kg] | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 8.50E+02 | 0.00E+00 | 0.00E+00 |
| Materials for energy recovery (MER) [kg] | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 |
| Exported electrical energy (EEE) [MJ] | 0.00E+00 | 1.88E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 |
| Exported thermal energy (EET) [MJ] | 0.00E+00 | 3.39E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 |

Caption: HWD = Hazardous waste disposed; NHWD = Non-hazardous waste disposed; RWD = Radioactive waste disposed; CRU = Components for re-use, MFR = Materials for recycling; MER = Materials for energy recovery; EEE = Exported electrical energy; EET = Exported thermal energy

Table 15: Biogenic carbon content of product and packaging for 1 tonne of Pre-painted Galvalume

| 4. Biogenic carbon content | | | | | | | |
|---|----------|----------|----------|----------|----------|----------|----------|
| Parameters | A1-A3 | A5 | C1 | C2 | C3 | C4 | D |
| Biogenic carbon content in product [kg] | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 |
| Biogenic carbon content in packaging [kg] | 5.59E-02 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 | 0.00E+00 |

Table 16: Additional Environmental parameters for 1 tonne of Pre-painted Galvalume




| 5. Optional indicators | | | | | | | |
|---|----------|----------|----------|----------|----------|----------|-----------|
| Parameters | A1-A3 | A5 | C1 | C2 | C3 | C4 | D |
| Particulate matter [Disease incidences] | 7.34E-04 | 1.59E-09 | 0.00E+00 | 7.88E-08 | 0.00E+00 | 2.01E-07 | -4.91E-05 |
| Ionising radiation, human health [kBq U235] | 1.93E+01 | 1.91E-03 | 0.00E+00 | 8.74E-04 | 0.00E+00 | 3.31E-02 | 2.66E+01 |
| Ecotoxicity, freshwater [CTUe] | 7.45E+03 | 2.29E-01 | 0.00E+00 | 1.69E+01 | 0.00E+00 | 1.73E+01 | -9.14E+02 |
| Human toxicity, cancer [CTUh] | 5.43E-07 | 1.25E-11 | 0.00E+00 | 2.87E-10 | 0.00E+00 | 2.53E-09 | -7.84E-07 |
| Human toxicity, non-cancer [CTUh] | 3.59E-05 | 1.25E-09 | 0.00E+00 | 1.17E-08 | 0.00E+00 | 2.79E-07 | -1.74E-05 |
| Land Use [Pt] | 3.71E+03 | 8.40E-02 | 0.00E+00 | 1.86E-01 | 0.00E+00 | 6.08E+00 | 2.10E+02 |

Caption: PM = Particulate matter emissions; IR = Ionising radiation, human health; ETF= Eco-toxicity (freshwater); HTP-c = Human toxicity, cancer effects; HTP-nc = Human toxicity, non-cancer effects; SQP = Soil quality potential/Land use related impacts

4.9 Interpretation

The interpretation of the results for 1 tonne of Pre-painted Galvalume Product are presented in Table 17.

Table 17: Interpretation of most significant contributors to life cycle parameters (Pre-painted Galvalume)

| Parameter | | Most significant contributor |
|---|---|--|
| Abiotic Depletion Potential (ADP) - Elements |  | The total cradle to gate impact is 1.12E-01 kg Sb eq. In A1 – A3 module more than 99% impact is coming from Galvanizing shop (due to the zinc (99.6%)). A total credit of 3.58E-03 kg Sb eq. is taken in module D. |
| Acidification Potential (AP) |  | The total cradle to gate impact is 3.75E+01 Mole of H+ eq. In A1 – A3, major impact is coming from HRC (65.3%), followed by Galvanizing shop (22.8%) (due to aluminium (68%) and electricity (19.5%)) and Colour coating shop (4.58%) (due to electricity (34.2%)). A total credit of 2.58E+00 Mole of H+ eq. is taken in module D. |
| Eutrophication Potential (EP) |  | The total cradle to gate impact is 3.71E-03 kg P eq. In A1 – A3, major impact is coming from HRC (68%), followed by Galvanizing shop (17.7%) (due to aluminium (65.7%), electricity (18.9%)) and Colour coating shop (7%) (due to electricity (16.9%)). A total credit of 3.14E-04 kg P eq. is taken in module D. |
| Climate Change - total [kg CO ₂ eq.] |  | The total cradle to gate impact is 4.32E+03 kg CO ₂ eq. In A1 – A3, major impact is coming from HRC (69%), followed by Galvanizing shop (16.8%) (due to aluminium (65.7%), electricity (17.2%)) and Colour coating line (6.9%) (due to polyurethane (19.3%)). A total credit of 1.45E+03 kg CO ₂ eq. is taken in the module D. |
| Ozone Layer Depletion Potential (ODP, steady state) |  | The total cradle to gate impact is 1.84E-06 kg CFC-11 eq. In module A1 – A3, major impact is coming from HRC (100%). A total credit of 3.44E-12 kg CFC-11 eq. is taken in module D. |
| Photochemical Ozone Creation Potential (POCP) |  | The total cradle to gate impact is 1.63E+01 kg NMVOC eq. In module A1 – A3, major impact is coming from HRC (64.7%), followed by galvanizing shop (22.8%) due to aluminium (66%) and Colour coating line (7.36%) due to polyurethane (22.6%). A total credit of 2.22E+00 kg NMVOC eq. is taken in module D. |
| Abiotic depletion potential (ADP) - Fossil |  | The total cradle to gate impact is 4.55E+04 MJ. In A1- A3 module, major impact is coming from HRC (63.2%), followed by Galvanizing shop (16.9%) due to aluminium (61.2%) and Colour coating line (11.4%) due to polyester resin (22.7%). A total credit of 1.41E+04 MJ is taken in module D. |

Concluding, the study provides fair understanding of environmental impacts during the various life cycle stages of steel production. It also identifies the hot spots in the value chain where improvement activities can be prioritised and accordingly investment can be planned. The scope covers the ecological information to be divided into raw material production (A1), transportation (A2), Manufacturing (A3), treatment of packaging (A5), transport of dismantled product to EoL site (C2), waste processing (C3), waste disposal (C4) as well as the end of life stage recycling (D) considerations.

5. LCA Terminology

| | |
|------------------------|---|
| Cradle to Gate | Scope of study extends from mining of natural resources to the completed product ready for shipping from the manufacturing dispatch “gate”, known as Modules A1-A3. |
| Cradle to Grave | Scope of study extends from mining of natural resources to manufacture, use and disposal of products at End of Life, including all Modules A-D. |
| End of life | Post-use phase life cycle stages involving collection and processing of materials (e.g., scrap) and recycling or disposal, known as Modules C and D. |

6. Other Environmental Information

The constituent materials used within our products are responsibly sourced and we apply the principles of Sustainable Development and of Environmental Stewardship as a standard business practice in our operations. Protecting the environment by preserving non-renewable natural resources, increasing energy efficiency, reducing the environmental emissions, limiting the impact of materials transportation to and from our operations is part of our way in doing business.

7. References

- EN 15804: 2012+A2:2019, Sustainability of construction works - Environmental product declarations - Core rules for the product category of construction products
- GaBi 10 2021: Dokumentation der GaBi-Datensätze der Datenbank zur Ganzheitlichen Bilanzierung. LBP, Universität Stuttgart und PE International, 2012
- GaBi 10 2021: Software und Datenbank zur Ganzheitlichen Bilanzierung. LBP, Universität Stuttgart und PE International, 2012
- ISO 14020:2000 Environmental labels and declarations - General principles
- ISO 14025:2006 Environmental labels and declarations - Type III environmental declarations - Principles and procedures
- ISO 14040:2006 Environmental management- Life cycle assessment - Principles and framework
- ISO 14044:2006 Environmental management - Life cycle assessment - Requirements and guidelines.
- ISO/TR 14049:2012 Environmental management – Life cycle assessment – Illustrative examples on how to apply ISO 14044 to goal and scope definition and inventory analysis.
- WSI and Eurofer’s Co-product Allocation Methodology 2014 - A methodology to determine the LCI of Steel industry Co-products.
- World Steel Association - CO₂ Data Collection User Guide, Version 9 (May 2019).
- PCR 2019:14, Product Category Rules (PCR) for 'CONSTRUCTION PRODUCT' Version 1.2.5.